

NASA TECHNICAL NOTE



NASA TN D-1911

NASA TN D-1911

LOAN COPY: RET
AFWL (WLIL)
KIRTLAND AFB, N

0154298



TECH LIBRARY KAFB, NM

FLUORINE UPTAKE OF FLUOROCARBON GREASES

by Patricia M. O'Donnell

Lewis Research Center

Cleveland, Ohio

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION • WASHINGTON, D. C. • DECEMBER 1964



FLUORINE UPTAKE OF FLUOROCARBON GREASES

By Patricia M. O'Donnell

Lewis Research Center
Cleveland, Ohio

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

For sale by the Office of Technical Services, Department of Commerce,
Washington, D.C. 20230 -- Price \$0.50

FLUORINE UPTAKE OF FLUOROCARBON GREASES

by Patricia M. O'Donnell

Lewis Research Center

SUMMARY

The fluorine uptake of four fluorocarbon greases was studied in a glass apparatus at 100° C and a fluorine pressure of 110 millimeters of mercury. The reactivity varied with the composition of the greases. The lowest fluorine uptake was observed with a grease formulated with polychlorotrifluoroethylene as the base material and a perfluorocarbon filler. When the same base material was retained but the filler was changed to a silica filler, a high fluorine uptake was observed.

INTRODUCTION

Fluorocarbon greases can be used satisfactorily in systems handling gaseous fluorine; however, the formulation of these greases is an important factor in determining their reactivity. It was the object of this experiment to determine the reactivity of four fluorocarbon greases with gaseous fluorine at 100° C and 110 millimeters of mercury.

PROCEDURE

The glass apparatus used to study the fluorine uptake of the greases is shown schematically in figure 1. The grease samples were weighed in porcelain boats and placed in a quartz reaction tube, which was then heated to the appropriate temperature, and fluorine was introduced to the desired pressure. The weight of fluorine consumed was calculated from the drop in pressure in the system of known volume. As fluorine was consumed, more fluorine was added to the reaction section to maintain the pressure to within 2 millimeters of mercury of the initial value.

RESULTS

The four fluorocarbon greases exposed to fluorine were KEL-F, KEL-F-90, KFL 1477, and 3ML 1429. The first three greases all have polychlorotrifluoroethylene as their base material. KEL-F and KEL-F-90 are silica filled, whereas KFL 1477 has a perfluorocarbon filler. Grease 3ML 1429 has a perfluorocarbon base material and a perfluorocarbon filler. The fluorine uptake of these four

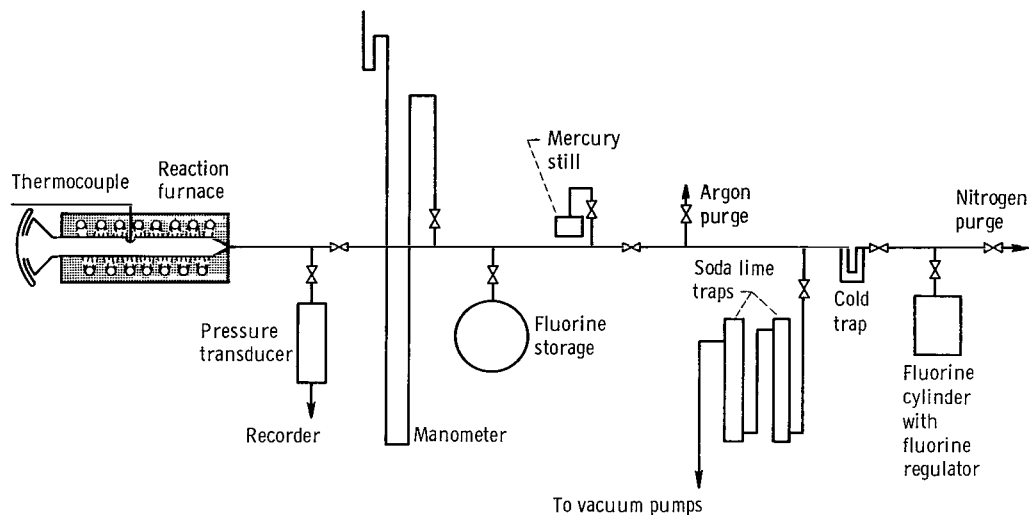


Figure 1. - Apparatus for determination of fluorine uptake of fluorocarbon greases.

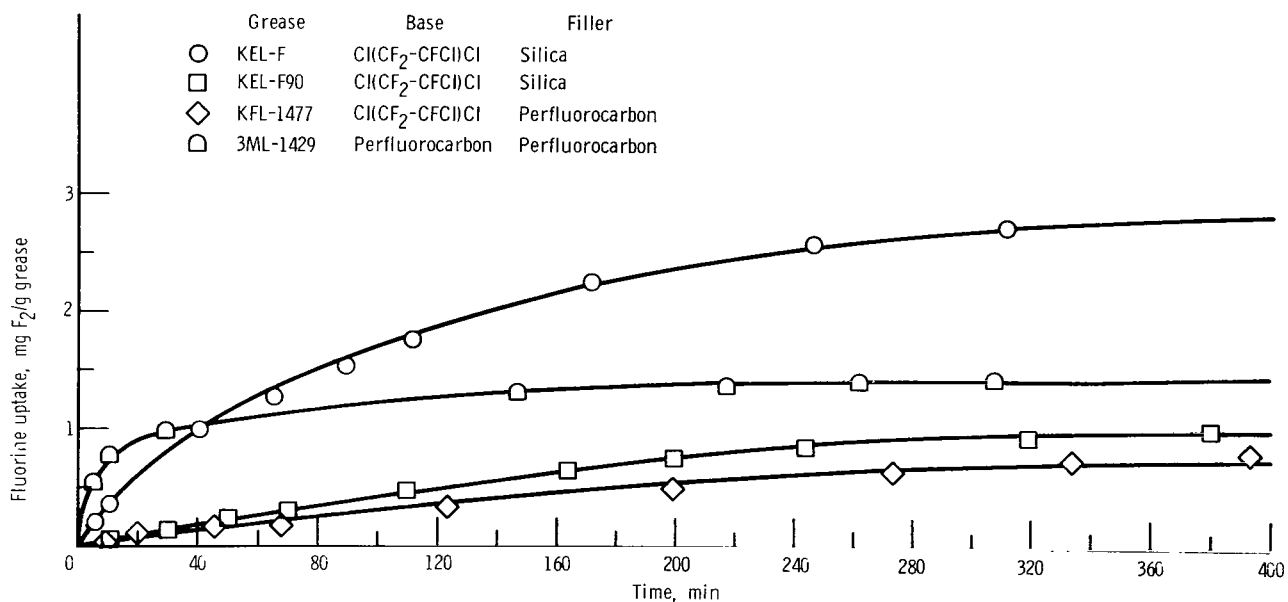


Figure 2. - Fluorine uptake by fluorocarbon greases at 100° C and fluorine pressure of 110 millimeters of mercury.

greases and their formulations are given in figure 2.

DISCUSSION

In a previous experiment (ref. 1) where copper was reacted with fluorine, the presence of cupric chloride (CuCl_2) was identified, and it was found that the fluorine had replaced some of the chlorine from the polychlorotrifluoroethylene base material of the grease that had been used as a lubricant in the system. The possibility of fluorine reacting with the silica filler could explain why KEL-F and KEL-F90 are more reactive than KFL 1477. The reactivity of

3ML 1429 is relatively high despite its completely fluorinated composition. It was determined by weight loss measurements that, after 400 minutes at 100° C and a fluorine pressure of 110 millimeters of mercury, KEL-F, KEL-F90, and KFL 1477 had lost 3 percent of their weight, whereas 3ML 1429 had lost 80 percent of its weight. These weight losses were determined by weighing the grease samples in the boat before and after a run. The vaporized products condensed at the cool ends of the reaction vessel. Similar weight losses of 3 and 82 percent were observed in blank runs using argon gas; however, there was no detectable pressure change in these blank runs. It is possible that fluorine uptake is partly or entirely a vapor phase reaction and hence proceeds more extensively with 3ML 1429. This is consistent with the earlier leveling off of the 3ML 1429 curve. It would be interesting to investigate the mechanisms of these reactions further.

Lewis Research Center
National Aeronautics and Space Administration
Cleveland, Ohio, August 5, 1964

REFERENCE

1. O'Donnell, Patricia M., and Spakowski, Adolph E.: Reaction of Copper and Fluorine from 800° to 1200° F. NASA TN D-768, 1961.

OK
2/6/85

"The aeronautical and space activities of the United States shall be conducted so as to contribute . . . to the expansion of human knowledge of phenomena in the atmosphere and space. The Administration shall provide for the widest practicable and appropriate dissemination of information concerning its activities and the results thereof."

—NATIONAL AERONAUTICS AND SPACE ACT OF 1958

NASA SCIENTIFIC AND TECHNICAL PUBLICATIONS

TECHNICAL REPORTS: Scientific and technical information considered important, complete, and a lasting contribution to existing knowledge.

TECHNICAL NOTES: Information less broad in scope but nevertheless of importance as a contribution to existing knowledge.

TECHNICAL MEMORANDUMS: Information receiving limited distribution because of preliminary data, security classification, or other reasons.

CONTRACTOR REPORTS: Technical information generated in connection with a NASA contract or grant and released under NASA auspices.

TECHNICAL TRANSLATIONS: Information published in a foreign language considered to merit NASA distribution in English.

TECHNICAL REPRINTS: Information derived from NASA activities and initially published in the form of journal articles.

SPECIAL PUBLICATIONS: Information derived from or of value to NASA activities but not necessarily reporting the results of individual NASA-programmed scientific efforts. Publications include conference proceedings, monographs, data compilations, handbooks, sourcebooks, and special bibliographies.

Details on the availability of these publications may be obtained from:

SCIENTIFIC AND TECHNICAL INFORMATION DIVISION
NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

Washington, D.C. 20546